


Influence of parameters variations on AlSi10Mg samples manufactured by SLM technology

Federico Uriati¹, Filippo Da Rin Betta¹, Paolo Ferro¹, Stefano Rosso¹, Gianpaolo Savio², Gianmaria Concheri², Filippo Berto³ and Roberto Meneghella²

¹ Department of Engineering and Management, University of Padova
² Department of Civil, Environmental and Architectural Engineering, University of Padova
³ Department of Mechanical and Industrial Engineering, NTNU Norwegian University of Science and Technology

Abstract Additive manufacturing technology, applied to metallic materials, offers new design possibilities: higher shape complexity, deeper material microstructure and mechanical performances control are allowed, compared to traditional processes. The aim of the project is to investigate the influence of different printing parameters in selective laser melted AlSi10Mg aluminium alloy and to correlate Energy Density (Ed) to microstructure, porosity, Ultimate Tensile Strength (UTS) and fatigue resistance. These results are carefully analysed in order to find optimal processing conditions that guarantee the maximum material density and the best mechanical properties.

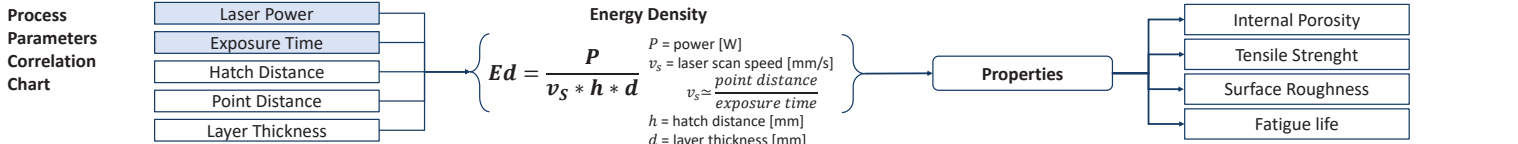

Strong and complex interaction between process parameters, building strategy, microstructure and mechanical properties characterises the SLM process. Laser Power and Exposure Time are varied within three experimental campaigns: (I) Hatch Distance, Point Distance and Layer Thickness are constant, (II) Iso-Energy Density, (III) Different Hatch Distance and Point Distance values from (I).

Materials & Methods

Chemical composition of AlSi10Mg: Al 91.50 Si 7.50 Cu 0.50 Ni 0.10 Fe 0.10 Mn 0.10 Mg 0.10 Zn 0.10 Pb 0.10

SLM Machine: **Renishaw AM400**
 Particle size : **15-45 μm**
 Platform dimension: **250 mm x 250 mm x 300mm**
 Laser maximum beam power: **400 W**
 Spot diameter (Ø): **70 μm**
 Gas: **Argon**

Platform temperature: **170 °C**
 Layer thickness (d): **30 μm**
 Point distance (s): **80 μm**
 Hatch distance (h): **80 μm**
 Laser power (P): **275 W**
 Exposure time (t): **40 μs**

Laser Scanning Strategy

Process parameters are selected within: 200 W to 375 W (laser power), 30 μs to 120 μs (exposure time), 61 μm to 80 μm (hatch distance=point distance).

Specimens

Metallography Investigation

As built Roughness	Avg: 22,86 [μm]	SD: 10,2 [μm]
--------------------	-----------------	---------------

Tensile testing

EN ISO 6892-1-2016

As built Roughness	Avg: 16,93 [μm]	SD: 6,1 [μm]
--------------------	-----------------	--------------

Fatigue testing



ASTM E466-15

Roughness after machining	Avg: 1,9 [μm]	SD: 0,6 [μm]
---------------------------	---------------	--------------


Experimental Results

Microstructure morphology induced by SLM process:

- gas porosity
- defect induced by 'balling'
- α-Al dendrites inside an eutectic matrix constituted by α-Al and Si-particles

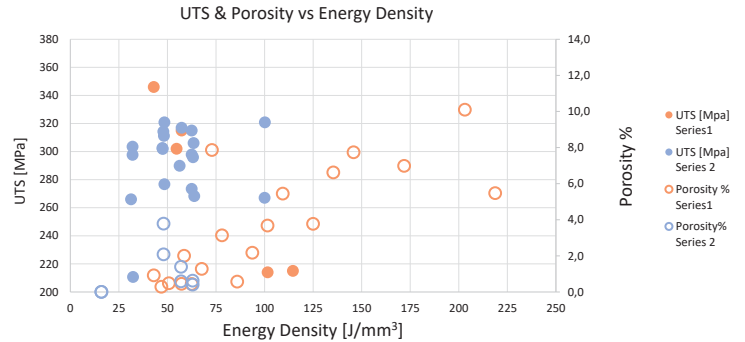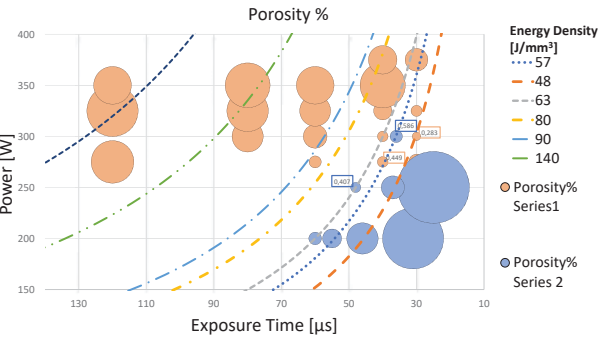

The material tensile strength is correlated to microstructure morphology:
 - a **direct proportionality** is shown between **energy density** and **porosity**; a minimum pores fraction is found at energy density equal to approximately 50 J/mm³;
 - an **inverse proportionality** between **UTS** and **porosity** is assessed.

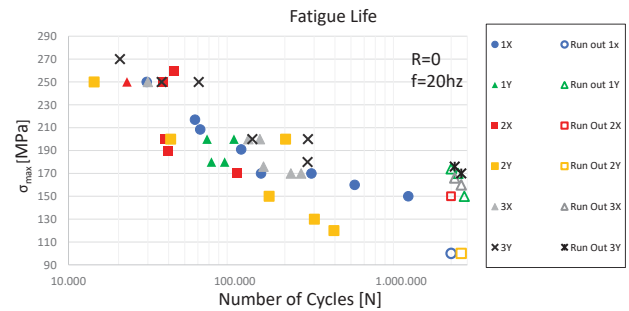

The fatigue resistance is characterized by a high scatter of results: two distinct behaviour are observed among samples manufactured in X, Y directions, under three different combination of laser power, exposure time, hatch distance and point distance.

Conclusions The strong influence of process parameters on microstructural and mechanical properties is confirmed: gas porosity is the main defect detected in the microstructure. Porosity and UTS are heavily correlated; the energy density helps in understanding the effects of laser power and exposure time on porosity while it fails in describing the complex interaction with mechanical properties. Fatigue life assessment requires further investigation to validate the optimal building strategy.

Acknowledgements This work was partially funded by the research grant FSE 2105-37-11-2018: Hybrid manufacturing strategies through selective laser sintering for the customization of series components from Regione Veneto, and by the research project FESR D23D18000160007 of Tesolin S.p.A.: Applicazione della tecnica additiva nella realizzazione di inserti per stampaggio a freddo from Regione Friuli Venezia Giulia.

References

- ASTM F2792-12a: Standard Terminology for Additive Manufacturing Technologies, (2012)
- Gibson, I., Rosen, D., Stucker, B.: Additive Manufacturing Technologies: 3D Printing, Rapid Prototyping, and Direct Digital Manufacturing. (2015)
- Kempfen, K., Thijis, L., Van Humbeeck, J., Kruth, J.P.: Mechanical Properties of AlSi10Mg Produced by Selective Laser Melting. Phys. Procedia. 39, 439-446 (2012)
- Read, N., Wang, W., Essa, K., Attallah, M.M.: Selective laser melting of AlSi10Mg alloy: Process optimisation and mechanical properties development. Mater. Des. 65, 417-424 (2015)